

Biosynthesis of Silver Nanoparticle Using Aqueous Extract of *Hibiscus Rosasinensis* Leaves

Samreen Fatema, Abdul Ahad, Mazahar Farooqui, and Pathan Mohd Arif*

Postgraduate and research center, Maulana Azad college of art's science and commerce,

Aurangabad (MS), India 431001.

arif7172@rediffmail.com

Abstract

The present study is for the green formation of silver nanoparticles by *Hibiscus rosasinensis* leaves extract. After successful formation of silver nanoparticles, Confirmation of Ag nanoparticles was carried out by using various characterizations techniques viz. structural by FT-IR, X-Ray Diffraction (XRD), morphological by Scanning Electron Microscopy (SEM), Atomic Force Microscopy (AFM) and elemental by Energy Dispersive X-ray Spectroscopy (EDX). The silver nanoparticles are also characterized for antibacterial activity. Staphylococci aures, Streptococci pyogens, Salmonella typhy.

Keywords: *Hibiscus rosasinensis*, Silver nanoparticle, Bioactivity of silver nanoparticles.

Introduction

From the ancient Babylonians and Greeks period, silver is extensively used as an antimicrobial agent [1]. Nanoparticle possess completely new or improved properties based on specific characteristics such as shape, size etc [2]. Nanoparticles have been investigated because it has unique properties which are different than bulk material [3]. Number of green methods has been developed for the synthesis of nanoparticle such as synthesis from chemical method [4] using plant extract [5] fungi [6, 7], microbes [8], and polysaccharides [9]. But for the synthesis of silver nanoparticles using plant extracts can be advantageous over other biological process of maintaining cell cultures [10] The biosynthesis of nanosilver crystals has been successfully reported using different plant extract such as leaf extracts of *Rosa rugosa* [11], *Coriandrum sativam* leaf extract [12], *Ocimum sanctum* [13] *Argemone Mexicana* [14], *Ocimum* [15] *Aspergillus niger* [16], *Iresine herbstii* leaf extract [17] The plant extract mediated synthesized silver nanoparticles shows enhanced antibacterial properties. When nanoparticles enter into the cell, it interferes with the bacterial growth signaling pathway by modulating tyrosine phosphorylation of putative peptides substrate critical for cell viability and division [18]. These properties make them useful in topical ointment and creams to prevent infection of burns and open wounds [19]. The factor on which antibacterial property depends is the shape of nano silver, surface coating, and surface charge. The activity of nano silver is solely due to silver ion releases. A low concentration of silver ions directly absorbed as coating on silver nanoparticle with smaller size is more effective because of higher specific surface and is faster release of silver ion [20]. To the best of our knowledge till date no body have used *Hibiscus rosasinensis* for the synthesis of silver nanoparticles.

Material and method

Green synthesis of silver nanoparticles was performed as describe in the literature [21].

Result and Discussion:

IR spectra of the silver nanoparticle: The FTIR measurement is carried out to identify the possible molecules, which are responsible for the reduction of silver to silver ion. The FTIR spectrum (Fig 1) of the silver nanoparticles synthesized from aqueous extract of *Hibiscus rosasinensis* leaves shows various bands, 3900, 3772, 3691, 3544, 3251, 3193, 3116, 2950, 2865, 2356, 979,948 and 744 cm⁻¹. Out of which 3544 corresponds to (H-bonded hydroxyl group), 2050 (-OH stretching) [22], 979 cm⁻¹ is for secondary amines [23].

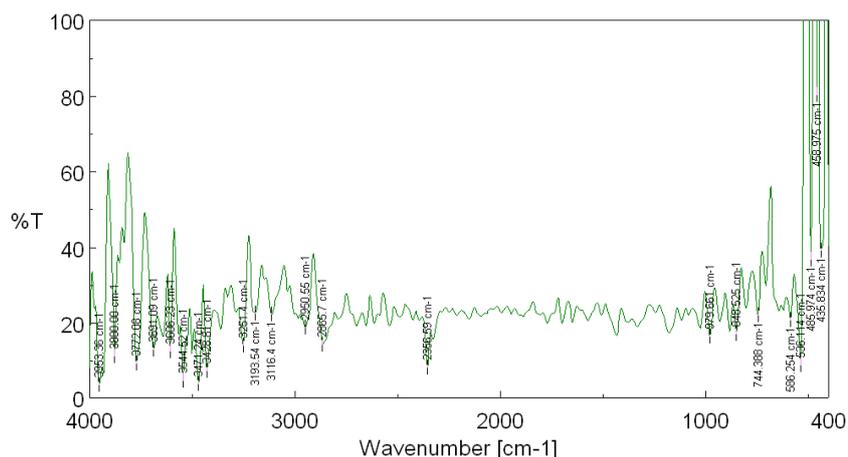


Fig1: FT-IR spectra of silver nanoparticles

X-ray diffraction

The XRD pattern of *Hibiscus rosasinensis* shows peak at (221) and (222) planes for silver. The Scherrer formula (Fig2) is used to calculate the particle size. $t = 0.94 \lambda / \beta \cos \theta$

The particle size of *Hibiscus rosasinensis* is found to be 11.80 nm. Some unexpected peaks are also obtained in the XRD of *Hibiscus rosasinensis*. It is also reported that a single peak corresponding to (222) plane has been observed in the diffraction pattern of silver nanoparticle synthesized by using aqueous solution of ficcus benghafensis leaf extract [24]. The extracts from plants may act both as reducing agent and capping agent in silver nanoparticle synthesis [25]. The water-soluble compounds present in the aqueous extract of plant materials were found to be responsible for efficient stabilization of nanoparticles and reduction of metal ions [26].

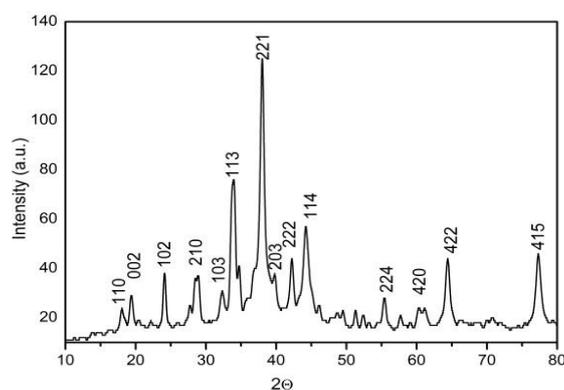


Fig2: X-ray Diffraction of Silver nanoparticle

Scanning Electron Microscope (SEM) and Atomic Force Microscope (AFM)

SEM images are used to study the morphology of silver nanoparticles (fig 3 & 4). It is observed that the size differences, size distribution, and capacity for aggregation depends on experimental conditions, stabilers, etc [27]. The shapes of silver nanoparticles, synthesized using plant extract, are like spheres, rods, prisms, plates, needles, leaf or dendrites. It depends on concentration of plant extract, part of the plant used, rate of addition or mixing of plant extract and metal salts, time taken for reaction, pH, temperature, etc [28]. In our case we are getting the shape of the nanoparticle like rods. The atomic force microscope is used to find out morphology of the surface. Experiments are also designed to evaluate surface tension of nano-material [29]. There is slight different between surface energy and surface tension. The surface energy is as reversible work per unit area

needed to create a new surface, whereas surface tension or surface stress is the reversible work per unit area needed to elastically stretch a pre-existing surface. Hence surface topology of living endothelial cells can be imaged by AFM [30].

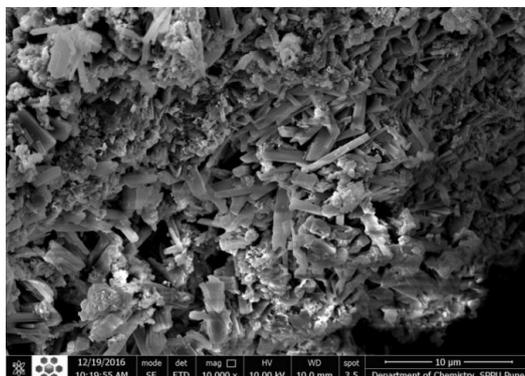


Fig3: SEM image of silver nanoparticle

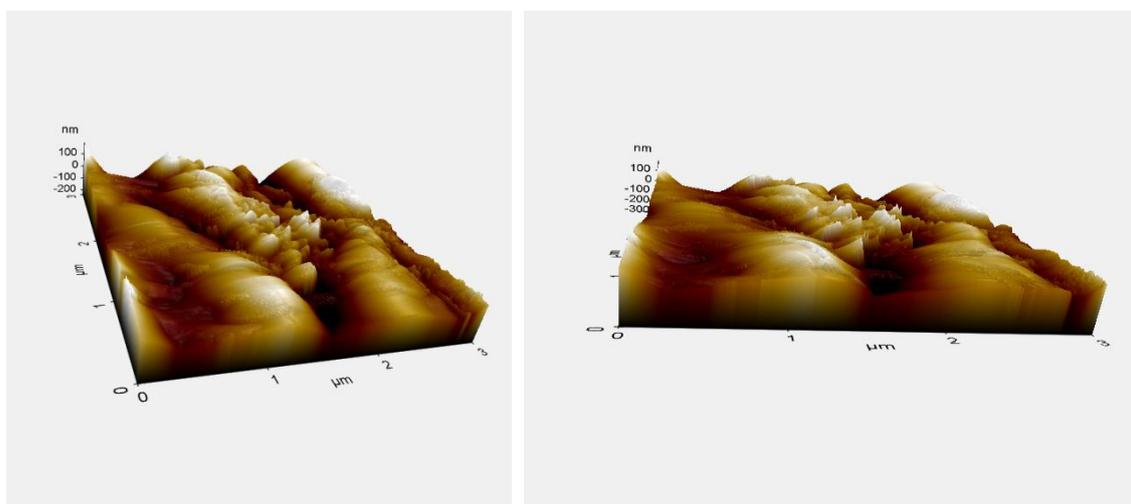


Fig4: AFM images of nanoparticle

Energy dispersive X-ray analysis EDX

Energy dispersive X-ray analysis shows the percentage of silver nanoparticle. EDX data shows the presence of carbon, sodium, and oxygen. The presence of carbon may be due to the phytochemicals which was added for the formation of silver nanoparticles and presence of sodium and oxygen may be from sodium carbonate which was added during the experiment.

Table 1: Percentage of atoms

Sr. No.	Atoms	% of atoms
1.	% of silver	51.90
2.	% of C	5.28
3.	% of Na	22.83
4.	% of O	56.90

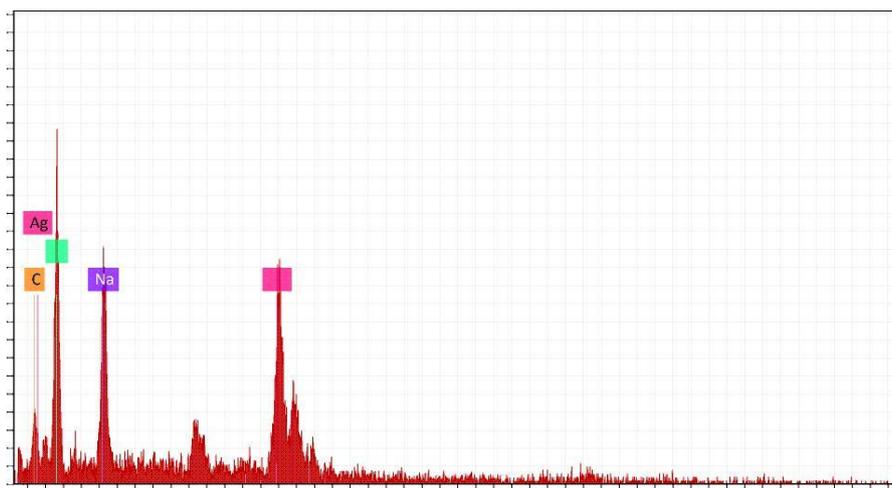


Fig 5: EDX spectra of silver nanoparticles

Antibacterial activity

The antimicrobial activity is measured by different ways, it include (i) zone of inhibition by disk diffusion and agar well diffusion method. (ii) minimum inhibitory concentration (MIC) by both macro-dilution and micro-dilution assay (iii) minimum bacterial concentration (MBC) (iv) growth pattern and (v) time kill curve [31]. The antibacterial activity is shown in table 2.

Table 2: Anti-bacterial activity of silver nanoparticles

	Bacteria	Activity
GM +ve Bacteria	<i>Staphylococi aures</i>	Highly active
	<i>Streptococci pyogens</i>	Highly active
	<i>Diplococci sp.</i>	Highly active
GM -ve Bacteria	<i>Escherichia coli</i>	Highly active
	<i>Pseudomonas fluroscens</i>	Highly active
	<i>Salmonella typhy</i>	Highly active

Conclusion

In conclusion, we succeed in the biosynthesis of silver nanoparticle by *Hibiscus rosasinensis* leaves, which have tremendous applications. The nanoparticles are then confirmed by instrumental analysis such as Fourier transformed infrared spectroscopy which shows the peaks for the compounds which are responsible for the reduction of silver to silver ions and act as capping agent. Scanning electron microscope and atomic force microscope gives the topological image of nanoparticle. EDX gives the percentage of the silver present, and XRD also confirms the formation of silver nanoparticles. The synthesized nanoparticles were investigated for the antibacterial activity, and it shows high activity against all tested bacteria, i.e., *Staphylococi aures*, *Streptococci pyogens*, *Diplococci sp.*, *Escherichia coli*, *Pseudomonas fluroscens*, *Salmonella typhy*

References:

1. C Krishnaraj, R Ramchandran, K Mohan, P T Kalaichelvan, (2012), Optimization for rapid synthesis of silver nanoparticles and its effect on phytopathogenic fungi. *Spectrochimica Acta Part A: Molecular and bio-molecular spectroscopy*. 93: 95-99.
2. R. Geethalakshmi, D.V.L Sarada, (2010), Synthesis of plant-mediated silver nanoparticles using *Trianthema decandra* extract and evaluation of their anti microbial activities, *International journal of engineering science and technology*. 2(5): 970-975.
3. Yadong Yin, Zhi-Yaun Li, Byron Gates, Younan Xia, Sagar Venkateshwaran, (2002), Synthesis of stable aqueous dispersion of silver nanoparticles through the Tollens process. *Journal of material chemistry*. 12: 522-527.
4. Digambar Malina, Agnieszka Sobczak-Kupiec, Zbigew Wzorek, Zygmunt Kowalski, (2012), Silver nanoparticles synthesis with different concentrations of polyvinylpyrrolidone. *Digest journal of nanomaterials and biostructures*. 7(4): 1527-1534.
5. S. Prathap Chandran, Minakshi Chaudhary, Renu Pasricha, Absar Ahmad and Murali Sastry, (2006), Synthesis of gold nanotriangles and silver nanoparticles using *Aloe vera* plant extract. *Biotechnology progress*. 22: 577-583.
6. A.K Gade, P.Bonde, A.P Ingle, P.D Marcate, N. Duran and M.K Rai, (2008), Exploitation of *Aspergillus niger* for synthesis of silver nanoparticles. *J of biobased mat and bioenergy*. 2: 1-5.
7. Mohammed Fayaz, K Balaji, P. T Kalaichelvan, R. Venkatesan, (2009), Fungal based synthesis of silver nanoparticles- An effect of temperature on the size of particle. *Collo and surf B: biointerfaces*. 74: 123-126.
8. Nalenthiran Pugazhenthiran, Sambandam Anamdan, Govindarajan Kathiravan, Nyagiru, Kannaian Udaya Prakash, Simon Crawford, Muthupandian Ashokkumar, (2009), Microbial synthesis of silver nanoparticles by *Bacillus* sp. *J. of nanopart res*. 11: 1811-1815.
9. Y. Park, Y.N Hong, A. Weyers, Y.S Kim, R.J Linhardt, (2011), Polysaccharides and phytochemical natural reservoirs for the green synthesis of gold and silver nanoparticle. *IET nano biotechnology*. 5 (3): 69-78.
10. Kouvaris P, (2012), Green synthesis and characterization of silver nanoparticles produced using *Arbutus unedo* leaf extract. *Material Letters*. 76: 18-20
11. Vyom Parashar, Rashmi Parashar, Bechan Sharma and Avinash Pandey, (2009), Parthenium leaf extract mediated synthesis of silver nanoparticles: A novel approach towards weed utilization. *Dig j. of nanopar and biostruc*. 4 (1): 45-50.
12. K. Satyavani, T. Ramanathan, S. Gurudeeban, (2011), Green synthesis of silver nanoparticles by using stem derived callus extract of bitter apple (*Citrullus colocynthis*). *Dig j. of nanomat and biostruc*, 6(3): 1019-1024.
13. Garima Singhal, Raju Bhavesh, Kunal Kasariya, Ashish Ranjan Sharma, Rajendra Pal Singh, (2011), Biosynthesis of silver nanoparticles using *Ocimum sanctum* (Tulsi) leaf extract and screening its antimicrobial activity. *Journal nanoparticle research*. 13: 2981-2988.
14. Singh, D. Jain, M.K Upadhyay, N. Khandelwal, H.N. Verma, (2010), Green synthesis of silver nanoparticles using *Argemone Mexicana* leaf extract and evaluation of their antimicrobial activities. *Digest journal of Nanomaterials and biostructure*. 5 (2): 483-489.

15. K. Mallikarjuna, G.Narasimha, G. R. Dillip, B. Praveen, B.Shreedhar, Sree Lakshmi, B.V.Reddy, B.Deva Prasad Raju, (2011), Green synthesis of silver nanoparticles using *Ocimum* leaf extract and their characterization. Digest journal of nanomaterials and biostructures. 6(1): 181-186.
16. A.K Gade, P.Bonde, A.P Ingle, P.D Marcato, N.Durain, and M.K Rai, (2008), Exploitation of *Aspergillus niger* for synthesis of silver nanoparticles. J. of biobased mat and bioenergy, 1(2): 1-5.
17. C.Dipankar, S. Murugan, (2012), The green synthesis, characterization, and evaluation of the biological activities of silver nanoparticles synthesized from *Iresine herbstii* leaf aqueous extract. Colli and surf B: Biointerfaces. 98: 112-119.
18. D Mubarak Ali, N Thajuddin, K Jeganathan, M Gvnasekaran, (2011), Plant extract mediated synthesis of silver and gold nanoparticles and its bacterial activity against clinically isolated pathogens. Colli and surf B: Biointerfaces. 85: 360-365.
19. Jae Yong Song, Beom Soo Kim, (2009), Rapid biological synthesis of silver nanoparticles using plant leaf extracts. Biopro biosyst Eng. 32: 79-84.
20. Richa Singh, Utkaesha U Shedbalkar, Sweety A Wadhvani, Balu A Chopde, Bacteriogenic silver nanoparticles: Synthesis mechanism, and applications. Applied microbiology biotechnology. DOI: 10.1007/s00253-6622-1.
21. Samreen Fatema, M. D.Shirsat, Mazahar Farooqui, Pathan Mohd Arif, (2019), Biosynthesis of silver nanoparticle using aqueous extract of *Saraca asoca* leaves, its characterization, and antimicrobial activity. International journal of nano dimension. 10(2): 163-168.K. Govindaraju, V.Kiruthiga, V.Ganesh Kumar and G. Singaravelu, (2009), Extracellular synthesis of silver nanoparticles by a Marine alga, *Sargassum wightii* Grevilli, and their antibacterial effect. Journal of nanoscience and nanotechnology. 9: 5497-5501.
22. Mohammad Fayaz, K. Balaji, P.T Kalaichelvan, R. Venkatesan, (2009), Fungal based synthesis of silver nanoparticles- An effect of temperature on the size of particles. Colloidal and surfaces B: Biointerfaces. 74: 123-126.
23. Antariksh Saxsena, R M Tripathi, Fahmina Zafar, Priti Singh, (2012), Green synthesis of silver nanoparticles using aqueous solution of *Ficus benghalensis* leaf extract and characterization of their antibacterial activity. Material latters. 67: 91-94.
24. Virender K Sharma, Ria A Yngard, Yekaterina Lin, (2009), Silver nanoparticles: Green synthesis and their anti-microbial activities. Advances in colloid and interface science. 145: 83-96.
25. P Prakash, P Gnan Prakasam, R Emmanuel, S Arokiyaraj, M Saravan, (2013), Green synthesis of silver nanoparticles from leaf extract of *Mimusops elengi* Linn for enhanced antibacterial activity against multidrug-resistant clinical isolates. Colloids and surfaces B: Biointerfaces. 108: 255-259.
26. Digmara Malina, Agnieszka Sobezak-Kupiec, Zbigniew Wzorek, Zygmuto Walski, (2012), Silver nanoparticles synthesis with different concentrations of polyvinyl pyrrolidone. Digest Journal of nanomaterials and biostructures. 7(4): 1532-1534.
27. Pantelis Kouvaris, Andreas Delimitis, Vassils Zaspalis, Dimitrios papadopoulous, Sofia A Tsipos, NikolaosMichailidis, Green synthesis and characterization of silver nanoparticles produced using *Arbutus Unedo* leaf extract.

28. Stephance Cuenot, Christian Fretigny, Sophie Demonstier, Champagne and Bernard Nysten, (2004), Surface tension effect on the mechanical properties of nano-materials measured by atomic force microscopy. *Physical review*. B69, 165410-(1-5).
29. Kenneth A Barbee, Peter F Davies, Ratneshwar Lae, (1994), Shear stress-induced reorganization of the surface topology of living endothelial cells imaged by atomic force microscopy. *Circulation research*. 74(1): 163-171.
30. Richa Singh, Utkasha U Shedbalkar, Sweety A Wadhvani, Balu A Chopde, Bacteriogenic silver nanoparticles: Synthesis mechanism, and applications. *Applied microbiology biotechnology*. DOI: 10.1007/s00253-6622-1.